




### 2.4. SiO<sub>2</sub> (Fortsetzung 2)

	Modifikation	Si-O [pm]	Si-O-Si [°]	$\rho$ g/cm <sup>-3</sup>	Lücke	gestopfte Varianten (Al → Si,+Kationen)
CN <sub>O</sub> = 2 CN <sub>Si</sub> = 4	$\alpha$ -Quarz	161	144	2.65		
	$\beta$ -Quarz	155	155	2.53	$\square_2\text{Si}_2\text{O}_4$	LiAlSiO <sub>4</sub> ( $\beta$ -Eucryptit)
	$\alpha$ -Tridymit	161	150	2.36		
	$\beta$ -Tridymit	(156)	(180)	2.26	$\square\text{Si}_2\text{O}_4$	KNa <sub>3</sub> (AlSiO <sub>4</sub> ) <sub>4</sub> (Nephelin)
	$\alpha$ -Cristobalith	161	147	2.27		
	$\beta$ -Cristobalith	161	(180)	2.33	$\square_2\text{Si}_2\text{O}_4$	KAlO <sub>2</sub> , H <sub>2</sub> O $\square\text{Si}_2\text{O}_4$ (Opal)
CN <sub>O</sub> = 3 CN <sub>Si</sub> = 6	fas. SiO <sub>2</sub> (W-SiO <sub>2</sub> )			1.97		Sr <sub>3</sub> Al <sub>2</sub> N <sub>4</sub>
	Coesit			2.91		
	Keatit			3.01		
	Stishovit	176-181		4.39		

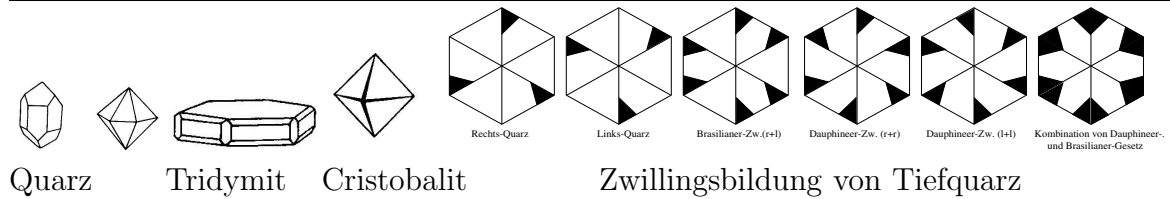


### 2.5.1. Pnictogen-Oxide


#### 2.5.1. P-Oxide: P<sub>4</sub>O<sub>10</sub>

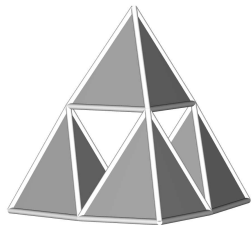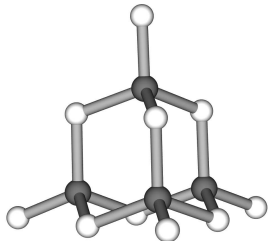

H-Form


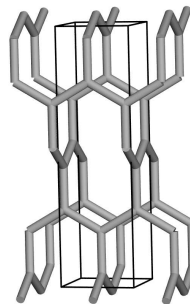


O-Form  
(Verknüpfungsschema der POO<sub>3/2</sub>-Tetraeder (entspr. Si-Teilgerüst in ThSi<sub>2</sub>))

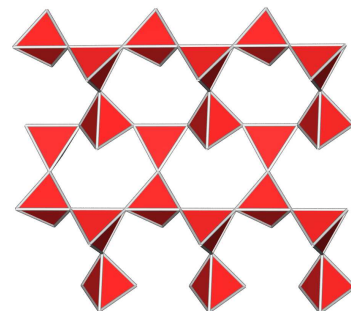


O'-Form

#### 2.5.2. As-Oxide

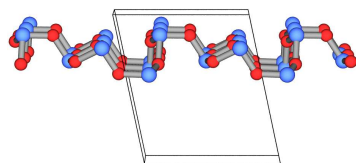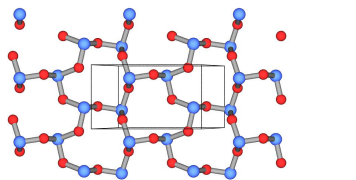


Claudetit As<sub>2</sub><sup>III</sup>O<sub>3</sub>

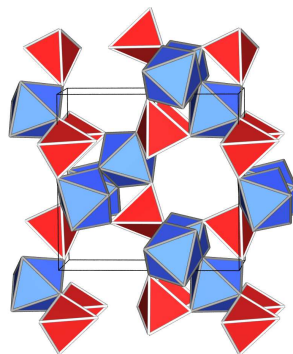

As<sub>2</sub>O<sub>5</sub> (As<sup>V</sup>O<sub>4/2</sub>)(As<sup>V</sup>O<sub>6/2</sub>)

#### 2.5.3. Sb-Oxide

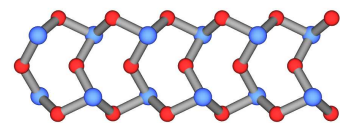

Valentinit Sb<sub>2</sub><sup>III</sup>O<sub>3</sub>